



ISSN (ONLINE): 2321-3051

INTERNATIONAL JOURNAL OF RESEARCH IN AERONAUTICAL AND MECHANICAL ENGINEERING

Optimal design of feeders for LM06 in Sand Casting: Comparative analysis for small, medium and large size dumbbell casting

Haider Hussain¹, Dr. A. I. Khandwawala²¹(Research Scholar, Bhagwant University Ajmer (Rajasthan), India)²(Ex. Professor, Mechanical Engineering Department, SGSITS, Indore, India)

Abstract:

In the sand casting technique, defect free casting had been the primary goal since the inception of the technology. In the present casting arena, emphasis on the precise and defect free casting has got greatly increased due to energy saving, environmental and economy considerations apart from the stringent product quality standard requirements. In order to achieve this level, computer simulation is inevitably necessary. FEM based simulation software is used to find solidification related defects specially Shrinkage Porosity very precisely. In the present work ANSYS, an FEM based versatile & low cost software has been used for hot spots identification in LM 06 dumbbells of different volumes in sand casting. The feeders have been designed and optimized by Conventional modulus approach and ANSYS 12.0 design optimizer tool. ANSYS has been used for transient thermal analysis and then optimization process has been performed. Path of two feeder optimization for sand casting on ANSYS have been searched by nodal analysis. Conductive and convective heat transfer has been taken in to consideration. The whole process is performed using traditional modulus approach also. The results are compared. The comparison reveals that ANSYS optimizer provides better results for casting having two feeders & three feeders. It saves material and energy thus resulting into economy and environmental benefits too. Hence it may be recommended as superior over modulus approach for two feeder system in sand casting of LM-06. The effect of increase of cast volume over feeder yield has also examined.

Keywords: - Sand Casting, LM06, Casting Defect, Shrinkage porosity, Feeder design optimization, Modulus Approach, FEM Analysis with ANSYS

1. INTRODUCTION

Sand casting is the most widely used process for both ferrous and non – ferrous metals, and accounts for approximately 90% of all castings produced [1]. In sand casting, sand mixed with binders and water is compacted around wood or metal pattern halves to produce a mould. The mould is removed from the pattern, assembled with cores and metal is poured in to the resultant cavities. After cooling, moulds are broken to remove the casting. After casting is removed from the sand moulds, sand mould is destroyed [2]. This leads to not only the loss of material but

also to the loss of energy required for molding and remolding the material again and again. In fact the repeated molding-remolding consumes huge amount of fuel ultimately contributing to the global warming which is the greatest havoc for modern civilization. Hence the optimal design of feeder system must be seen not only from the material saving point of view, it must simultaneously be pursued from the environmental considerations too [16]. The modern casting processes not only require high precision and accuracy, they require energy efficiency and environmental consistency too. The present work is a determined step in this direction.

In sand casting, molten liquid metal is poured into a cavity which takes the negative shape of the object and the mould is made from sands. Heat removal is by heat transfer in sand mould, the governing equations for heat transfer are [3]

$$\frac{\partial T}{\partial t} = \alpha \frac{\partial^2 T}{\partial x^2} \quad (1)$$

$$T(x, 0) = T_0 \quad (2) \quad T(0, t) = T_M \text{ (Temperature at metal end)} \quad (3)$$

$$T(\infty, t) = T_0 \quad (4)$$

Finite Element Method (FEM) is a powerful computational tool that is used to numerically solve many engineering problems. Most of the Research on the area of casting processes modeling uses FEM as a solver to the casting Process model. The numerical simulation of solidification process using either Finite Difference or Finite Element Methods (FDM/FEM) involves the following steps: [1]

1. Formulating an accurate mathematical model of the solidification process.
2. Specifying accurate values for thermal properties of material involved.
3. Performing the analysis to obtain the temperature history of casting and mould points.
4. Post – processing the results to visualize the solidification pattern and identify defects.

Feeders are designed to compensate the solidification shrinkage of a casting, and make it free of shrinkage porosity. Feeder design parameters include the number, location, shape and dimensions of feeder. Feed path and feeding distance influence the location and number of feeders. The volume of the feeders must be minimized to increase the yield. The criterion is given by for getting feeder yield C_{F3} :

$$C_{F3} = N_c v_c / (N_c v_c + \sum_i v_{fi}) \quad (5)$$

Finite element analysis based software ANSYS 12.0 has been used. Modal of casting is done in Pro E wild fire and cylindrical feeders have been created in ANSYS modeling. Element selection and material property feeding is done latter. Convective load have been considered after proper meshing. Proper boundary values of temperature have been provided and then transient thermal analyses have been performed. DB log file has been assigned to ANSYS optimizer and then design variable, state variable and objective functions have been provided [5]. They are height of feeder, maximum temperature difference of feeder and respective casting zone, inverse of feeder yield respectively with suitable allowances and factor of safety. First order optimization has been performed through ANSYS 12.0.

In FEM, the field variables are the temperatures at all nodal points that vary with time. Thermal properties like thermal conductivity, density, specific heat also vary with temperature and hence the problem becomes non – linear transient in nature Galerkin's weighted residual approach has been reported [7]. The advantage of using FEM is the ability to handle complex boundaries, the ease in implementing boundary condition. But this method requires much effort for formulation of problem, data preparation and need long processing time [8].

In general, FEM is preferred as it allows a wider choice of element shapes and better accuracy, while FDM based simulation programs are faster and easier to execute. Recent advances have been in the areas of automatic preprocessing (mesh generation), adaptive remeshing for better accuracy in critical regions, heat transfer models for considering the effect of variable air gap and mould coatings, convective and radiation heat transfer and improving

the efficiency of computation[9]. Feeder optimization has been performed using topology optimization [10], poison equation approximation [11] and genetic algorithm [12].

P. Prabhakara Rao gives advantages of computer simulation based design enumerated. The procedures thus described have been demonstrated with the above case study of application of Pro CAST simulation at G.S alloy Foundry. It is demonstrated that the foundries can derive mileage by resorting to FEM simulations of the casting process for process development and optimization. [13]

The application of casting simulation softwares in the foundries not only minimizes the wastages of resources required for final castings, but also improves / enhances the quality and yield of castings, which implies higher value addition and lower production cost. The experimental study represents the effect of sizes of risers and necks on the solidification behavior of the aluminum alloy castings. The simulated results are more or less similar with experimental results. [14]

The application of computer aided method, solid modeling, and casting simulation technologies in foundries can able to minimize the bottlenecks and non value added time in casting development, as it reduces the number of trial casting required on the shop floor. In addition, the optimization of riser neck reduces or completely removes the occurrence of shrinkage defect in the casting. The application of casting simulation software based on finite element method and vector element method shows good results and matched with the experimental results.[15]

2. DATA COLLECTION

Two feeder optimization has been performed on a dumbbell casting of Aluminium-06. Two feeders have been considered.

For Small size Dumbbell Casting:

Table: 01

S	Volume M^3	Surface Area M^2	Modulus= V/A
A	8.0×10^{-6}	2.4×10^{-3}	3.33×10^{-3}
B	1.131×10^{-6}	4.90×10^{-4}	2.3×10^{-3}
C	6.4×10^{-5}	9.6×10^{-3}	6.67×10^{-3}
D	1.131×10^{-6}	4.9×10^{-4}	2.3×10^{-3}

For Medium size Dumbbell Casting:

Table: 02

S	Volume M^3	Surface Area M^2	Modulus= V/A
A	2.16×10^{-4}	2.16×10^{-2}	0.01
B	1.5×10^{-5}	3.5×10^{-3}	4.3×10^{-3}
C	6.4×10^{-5}	9.6×10^{-3}	6.67×10^{-3}
D	1.5×10^{-5}	3.5×10^{-3}	4.3×10^{-3}

For Large size Dumbbell Casting:

Table: 03

S	Volume M^3	Surface Area M^2	Modulus= V/A
A	5.12×10^{-4}	3.84×10^{-2}	13.3×10^{-3}
B	2.41×10^{-5}	4.62×10^{-3}	5.22×10^{-3}
C	2.16×10^{-4}	2.16×10^{-2}	10×10^{-3}
D	2.41×10^{-5}	4.62×10^{-3}	5.22×10^{-3}

For Very Large size Dumbbell Casting:

Table: 04

S	Volume M^3	Surface Area	Modulus= V/A
A	1.6×10^{-3}	6×10^{-2}	0.0267
B	1.176×10^{-5}	6.13×10^{-3}	2.87×10^{-3}
C	1.25×10^{-4}	1.5×10^{-2}	6.67×10^{-3}
D	1.765×10^{-5}	6.126×10^{-3}	2.88×10^{-3}
E	3.9×10^{-6}	1.099×10^{-3}	3.547×10^{-3}
F	1.56×10^{-5}	3.75×10^{-5}	0.416
G	3.9×10^{-6}	1.0995×10^{-3}	3.55×10^{-3}

Feeders can be optimized by modulus approach. The thickest section has highest value of modulus [1]. The optimization can be performed on ANSYS12. [5]

3. FEEDER OPTIMIZATION

The use of negative of the gradient vector as a direction for minimization was first made by Cauchy in 1847. In this method we start from initial trial point X1 and iteratively move towards the optimum point.[4] The method of steepest descent may appear to be the best unconstrained minimization technique since each one-dimensional search starts in the best direction. Design optimization works entirely with the ANSYS Parametric Design Language (APDL) and is contained within its own module (/OPT). Design optimization is largely concerned with controlling user-defined, APDL functions/parameters that are to be constrained or minimized using standard optimization methods (e.g., function minimization, gradients, design of experiments). The independent variables in an optimization analysis are the design variables. The vector of design variables is indicated by: [4]

4. OPTIMIZATION OF DUMBBELL CASTING WITH MODULUS APPROACH AND ANSYS

For removing shrinkage porosity defect, two feeders are designed here by modulus approach and ANSYS 12.0 design optimizer for dumbbell casting. Dumbbell has been considered in four sections A, B, C, D. First modulus approach has been used and then ANSYS Optimizer applied.

Modulus Approach For small Dumbbell Casting with two feeders-

$$D_{f1} = 18.6 \text{ MM}$$

Height of Feeder = 27.9 MM

$$D_{f2} = 37.4 \text{ MM}$$

Height of Second Feeder = 56.10 MM

So feeder yield by Modulus method is = **51.77%**

Modulus Approach For medium size Dumbbell Casting with two feeders-

$$D_{f1} = 56.074 \text{ MM}$$

Height of Feeder = 84.11 MM

$$D_{f2} = 42.213 \text{ MM}$$

Height of Second Feeder = 63.3 MM

So feeder yield by Modulus method is = **51.12%**

Modulus Approach For Large size Dumbbell Casting with two feeders-

$$D_{f1} = 84.336 \text{ MM}$$

Height of Feeder = 126.50 MM

Similarly for second feeder calculations have been done.

So feeder yield by Modulus method is = **42.37%**

Modulus Approach for Large size Dumbbell Casting with three feeders-

$$D_{f1} = 212 \text{ MM}$$

$$H_{f1} = 317 \text{ MM}$$

$$D_{f2} = 64.97 \text{ MM} , H_{f2} = 97.46 \text{ MM}$$

$$D_{f3} = 26.3 \text{ MM} , H_{f3} = 39.47 \text{ MM}$$

Total Volume of Casting/ Total Volume of Casting + Total Volume of Feeders

So feeder yield by Modulus method is = **13.36%**

The process of analysis of this case with Design optimizer of ANSYS 12.0 (An FEM Based general purpose software) has been search out for two feeders. Here we have taken height of feeders as a design variables, State variable S1 = FT1-CT1 (always positive), State variable S2 = FT2-CT2 (always positive) with suitable allowances and factor of safety so that hot spot must not remain in casted part. It should be in respective feeder. FT= maximum feeder temperature for respective zone, CT= maximum casting temperature of catchment. Following are the graphs as a result of optimization. Figure1 is showing the temperature according to cooling. It can be seen that higher temperature are with feeders as compare to casing. This assures that the shrinkage porosity will be in feeders only.

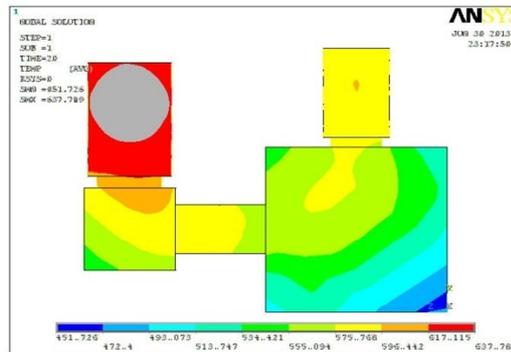


Figure 1: At centre plane of small dumbbell shape casting with optimized feeders

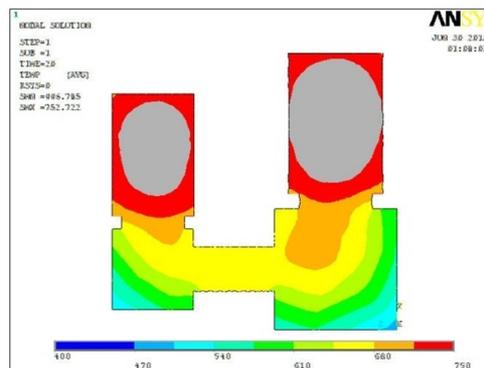


Figure 2: At centre plane of medium dumbbell shape casting with optimized feeders

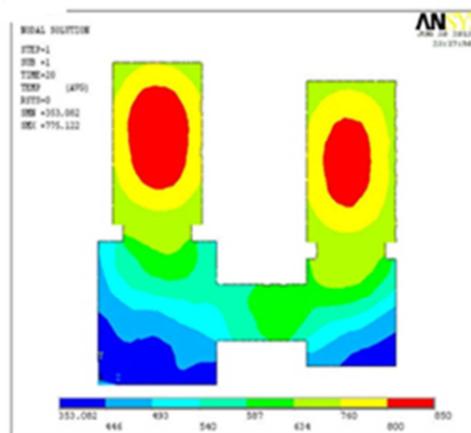


Figure 3: At centre plane of Very large dumbbell shape casting with optimized feeders

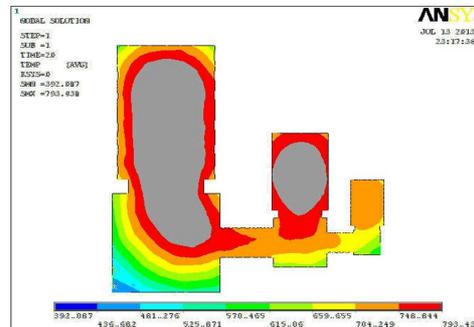


Figure 4: At centre plane of Very large dumbbell shape casting with optimized feeders

5. CONCLUSION

Feeder yield obtained comes out from modulus method for two feeder casting for small dumbbell is equal to = **51.77 %** and with FEM based ANSYS design optimizer is equal to = **86.88 %**. So net advantage gained by ANSYS 12.0 design optimizer is **35 %**. Feeder yield obtained comes out from modulus method for two feeder medium size dumbbell casting is equal to = **51.12%** and with FEM based ANSYS design optimizer is equal to = **58.8 %**. So net advantage gained by ANSYS 12.0 design optimizer is **08 %**. Feeder yield obtained comes out from modulus method for two feeder large size dumbbell casting is equal to = **42.37%** and with FEM based ANSYS design optimizer is equal to = **60.35 %**. So net advantage gained by ANSYS 12.0 design optimizer is **18 %**. Feeder yield obtained comes out from modulus method for two feeder large size dumbbell casting is equal to = **13.36%** and with FEM based ANSYS design optimizer is equal to = **50.76 %**. So net advantage gained by ANSYS 12.0 design optimizer is **37 %**. It can be seen that when volume of casting is low feeder yield is high as compare to high volume casting feeders. The advantage of FEM based ANSYS optimizer average 20 to 25 % percent over conventional modulus approach.

6. ACKNOWLEDGEMENTS

The authors are thankful to the Bhagwant University for providing the support & facility and friends and family members for their support.

REFERENCES

- [1] Ravi B., Metal Casting -computer aided design and analysis PHI, 2005.
- [2] Jain R.K., Production Technology, Khanna Publishers, Delhi, 15th Edition August,1995
- [3] Qin Rongshan, Workshop: Heat management, Lecturer 7, Graduate Institute of Ferrous Technology, POSTECH computational metallurgy laboratory Korea, lecturer notes, seen on web in dec., 2008.
- [4] Rao S.S., Optimization; Theory and Application, Wiley Eastern Limited, 1975.
- [5] ANSYS help - Thermal Tutorial, First order optimization, ANSYS Inc.
- [6] <http://www.mece.ualberta.ca/Tutorials/ANSYS>
- [7] Joshi Durgesh and Ravi B., comparison of finite element method and vector element method for casting solidification simulation, Indian Foundry Journal,22-23. vol. 54 no.9 September. 22-23, 2008, PP. 21-27.

- [8] Venkatesan A., Rajadurai A., Effect of Air-Gap on Casting Solidification, American Foundry Society, 2006, PP.191-199.
- [9] Ravi B. and Srinivasan M.N., casting solidification analysis by modulus vector method, International Journal of Cast Metals Res., 1996, PP.1-7.
- [10] Tavakoli R. And Davami P., Optimal riser design in sand casting process with evolutionary topology optimization, Struct multidisc optim, accepted on 8 June 2008, DOI 10.1007/s00158-008-0282-z, Springer – Verlag, 2008, PP. 1-10.
- [11] Tavakoli Rohalla and Davami Parviz , Optimal riser design in sand casting by topology optimization with SIMP method I : Poisson approximation of nonlinear heat transfer, equation, Struct multidisc optim , accepted on 29 October 2007, Springer – Verlag, 2008, PP. 193-202.
- [12] Elizabeth Jacob , Roschen Sasikumar , B. Praveen and V. Gopalakrishna , Intelligent design of feeders for castings by augmenting CAD with genetic algorithms, Journal of Intelligent Manufacturing , 15, 2004, PP.299-305.
- [13] P. Prabhakara Rao, G.Chakraverthi, A.C.S. Kumar, G. Srinivasa Rao, Modeling and Simulation of Solidification in Alloy Steel Sand Castings, International Journal of Thermal Technologies, Vol.1, No.1 Dec. 2011, PP.121-127.
- [14] T. Nandi, R. Behera, A. Chanda and G. Sutradhar, Study on Solidification Behaviour of LM6 Castings by Using Computer -Aided Simulation Software, Indian Foundry Journal, Vol. 57, No. 3, March 2011, PP.44-49.
- [15] Behera Rabindra, Kayal.S, Sutradhar. G, Solidification behavior and detection of Hotspots in Aluminium Alloy castings: Computer Aided Analysis and experimental validation, International Journal of Applied Engineering Research, Dindigul, Volume 1, No 4, 2011, PP.715-726 .
- [16] Belmira Neto, Carolien Kroeze, Leen Hordijk, Carlos Costad, Modelling the environmental impact of an aluminium pressure die casting plant and options for control, Environmental Modeling & Software, Volume 23, Issue 2, February 2008, PP.147–168